

§18. Effect of Bending on Critical Current of React-and-Jacket Processed Nb₃Sn Conductor

Takahata, K., Tamura, H., Mito, T., Imagawa, S.

A new large-scale Nb₃Sn conductor has been developed that has an aluminum-alloy jacket to support an electromagnetic force¹⁻⁴. The manufacturing process of the conductor is unique in that a jacketing process is performed after reaction heat treatment of the Nb₃Sn cable. This process, which we term the “react-and-jacket” process, imparts the conductor with a high critical current (I_c) because the compressive strain induced in the Nb₃Sn filaments due to the thermal contraction of the jacket material is reduced. This conductor will be wound after the reaction heat treatment to form a magnet. This manufacturing process, the so-called “react-and-wind” process, is more attractive than the conventional wind-and-react process used to fabricate large magnets (e.g., fusion magnets) with Nb₃Sn superconductors because it does not require a large furnace for the reaction heat treatment. However, the bending strain due to winding should be carefully controlled to prevent degrading I_c . This paper reports I_c measurements of a wound sample and discusses I_c degradation by the bending strain.

Fig. 1 shows a photograph of a cross-section of the developed conductor. The Rutherford cable consists of 18 bronze route Nb₃Sn wires with diameters of 1.0 mm. The heat-treated cable and indium sheets as fillers were embedded in the grooved aluminum-alloy jacket. The jacket cover was then welded by friction stir welding⁴, which does not damage the cable. The I_c of the conductor was estimated to be approximately 4.7 kA at 12 T.

A 3-m-long conductor sample was fabricated and wound flatwise in a three-turn coil (see Fig. 2). The coil has an inner radius of 150 mm. It was inserted into a split magnet and I_c was measured under external magnetic fields of up to 7.1 T. Fig. 3 shows the measured I_c . The filled circles indicate I_c for the conductor sample and the open circles indicate the product of I_c for a single strand and the number of strands (=18). The I_c of the conductor was 8.3 kA at 7 T. The product for 18 strands was 11.1 kA. Therefore, the degradation of I_c was found to be 25%.

Assuming that a current can flow between filaments with a relatively low resistance, I_c for single strand will equal the integral of the critical current density over the filament bundle region⁵. For the strain dependence of the critical current density, we used the empirical formula proposed by Godeke⁵⁻⁶. The triangles in Fig. 3 indicate the predicted I_c of the conductor. The measured I_c is slightly higher than the predicted one. This result demonstrates that the conductor can be wound in a coil configuration without excessive damage.

The calculation also predicts that a small outward shift of the neutral axis will degrade I_c . Therefore, the

bending neutral axis should be precisely controlled during coil manufacture. The tested conductor was bent by a bending machine with seven rollers so that its neutral axis was approximately coincident with the midline.

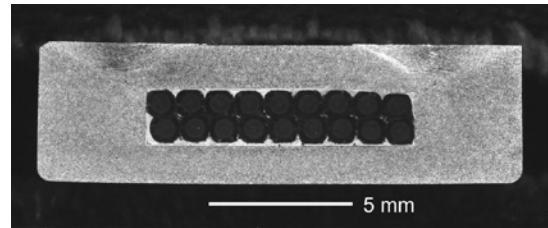


Fig. 1. Photograph of conductor cross-section.

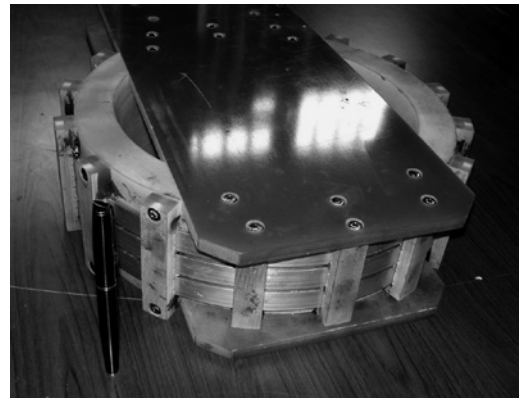


Fig. 2. Photograph of three-turn winding sample for I_c measurements.

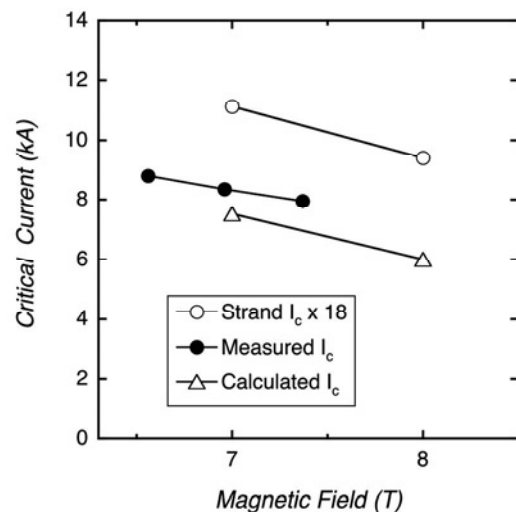


Fig. 3. Measured and predicted critical currents.

- 1) Takahata, K. et al.: *Cryogenics* **51** (2011) 397.
- 2) Tamura, H. et al.: *Plasma and Fusion Res.* **5** (2010) S1035.
- 3) Takahata, K. et al.: *Fusion Eng. Des.* **82** (2007) 1487.
- 4) Sugimoto, M. et al.: *IEEE Trans. Appl. Super.* (2011) DOI:10.1109/TASC.2011.2174813.
- 5) Takayasu, M. et al.: *Supercond. Sci. Technol.* **24** (2011) 045012.
- 6) Godeke, A. et al.: *Supercond. Sci. Technol.* **19** (2006) R100.